

02

The manifestation of local vibrations in photoluminescence spectra of ZnO:Fe³⁺

© V.I. Sokolov¹, N.B. Gruzdev¹, V.V. Menshenin¹, A.N. Kiryakov², A.F. Zatsepin², V.A. Vazhenin², G.A. Emelchenko³

¹M.N. Mikheev Institute of Metal Physics, Ural Branch, Russian Academy of Sciences, 620108 Yekaterinburg, Russia

²Ural Federal University after the first President of Russia B.N. Yeltsin, 620002 Yekaterinburg, Russia

³Osipyan Institute of Solid State Physics RAS, 142432 Chernogolovka, Russia

e-mail: visokolov@imp.uran.ru

Received September 24, 2022

Revised April 12, 2023

Accepted April 13, 2023

In this paper photoluminescence spectra and EPR-signals of ZnO single crystals, doped with manganese and containing (from EPR data) uncontrolled impurity of iron, were investigated. At the temperature of 4.5 K in photoluminescence spectrum the band in energy interval of 1.55–1.8 eV (12493–14508 cm⁻¹) was observed. This band contains some intensive lines; these lines are caused by Fe³⁺ ions (*d*⁵-configuration). The first and most intensive line at the energy of 1.79 eV corresponds to irradiative transition ⁴T₁ → ⁶A₁ in Fe³⁺ ions. The other peaks are electronic-vibrational structure. This structure may be caused by force interaction in deformed Fe³⁺-4O²⁻ cluster.

Keywords: zinc oxide, Fe³⁺ impurity, photoluminescence, EPR.

DOI: 10.61011/EOS.2023.04.56359.52-22

Introduction

A detailed study of the optical absorption of hydrothermal ZnO:Mn single-crystals was carried out in the papers [1,2]. In the EPR spectra of these crystals, along with signals from Mn²⁺ ions, signals belonging to an uncontrolled impurity of Fe³⁺ ions (*d*⁵ configurations) were detected. The signals of Fe ions ³⁺ were approximately two orders of magnitude weaker than the signals corresponding to ions Mn²⁺. They were significantly weakened when the crystal was illuminated with a xenon lamp, while the signals of Mn²⁺ ions did not respond to illumination. Fe³⁺ ion lines were observed in photoluminescence (PL) spectra in papers [3,4]. The authors of [3] have shown that in the PL spectrum of ZnO crystals, when excited by a two-watt Ar⁺ ion laser at a temperature of 1.8 K, there is a A line at an energy of 1.78742 eV (14406.6 cm⁻¹), which was interpreted as the intracenter transition ⁴T₁ → ⁶A₁ of the Fe³⁺(*d*⁵) ion. This line was accompanied by a large number of vibrational repetitions in energy interval of 1.66084–1.77468 eV (13386.37–14303.92 cm⁻¹). One of the replicas at the energy of 1.72417 eV (13896.81 cm⁻¹) was as intense and narrow as the zero-phonon line A. All the lines were identified as phonon replicas.

In the paper [4] PL spectrum was observed in the interval of 13250–14500 cm⁻¹ on single-crystal samples obtained by the hydrothermal method and the chemical gas transport method. The observed spectrum [4] was interpreted by the authors of [5] by analogy with the paper [3], assuming that

all vibrational replicas of the zero-phonon line are due to interaction with lattice phonons.

The aim of this paper is to reveal the contribution of the Fe³⁺-4O²⁻ cluster states to the luminescence spectrum of manganese-doped ZnO samples. The radius 3*d*⁵-configuration of the Fe³⁺ ion, according to [6], noticeably differs from the radius of the Zn²⁺ ion — by 0.11 Å. In addition, the Fe³⁺ ion has a positive charge relative to the lattice. This should result in significant changes in the force interaction in the Fe³⁺-4O²⁻ cluster and the formation of local oscillations.

Experiment description

In this paper, ZnO:Mn samples obtained by the hydrothermal method at the ISSP of RAS (Chernogolovka) were studied. Intentional doping of the samples with iron was not carried out, but the iron impurity was present in these samples as uncontrolled. It was found by observing the EPR signals corresponding to this impurity. The crystal grown was carried out during a month in a liquid medium containing lithium compounds. That is why there are also Li⁺ ions in the crystal. They are negatively charged in relation to the lattice, since, unlike the substituted zinc ion, they donate one electron, not two. To compensate for this charge, the residual iron Fe²⁺ (*d*⁶) ions donate one electron and end up in the state Fe³⁺ (*d*⁵). EPR signals were recorded on an EMX Plus Bruker spectrometer at

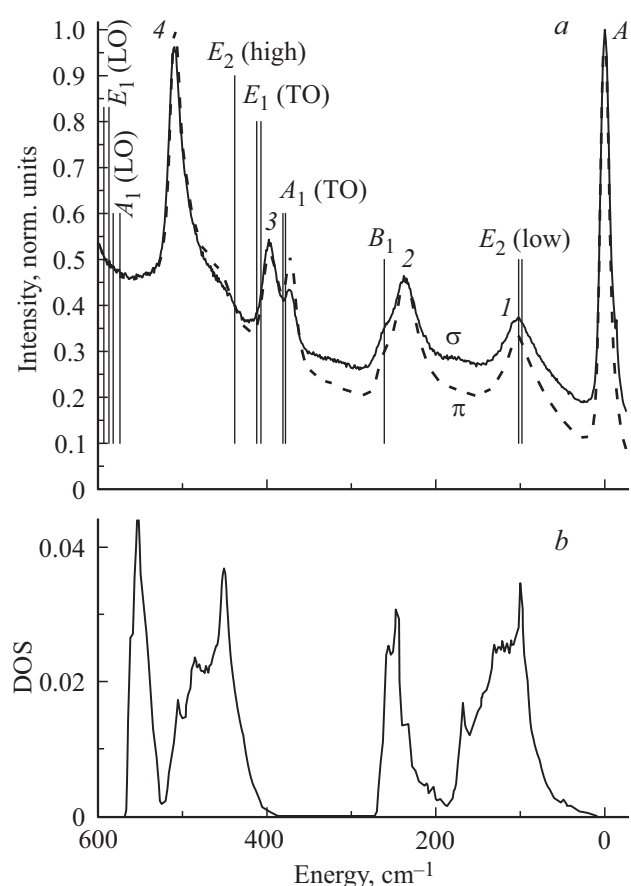


Figure 1. (a) PL spectra of ZnO:Mn, Fe single-crystals at $T = 4.5$ K for σ - (solid curve) and π polarization (dashed curve). Comparison of the energies of vibrational satellites of the zero-phonon line A with the energies of natural oscillations A_1 , B_1 , E_1 and E_2 of ions of the zinc oxide base unit, consisting of two zinc ions and two oxygen ions. The vertical lines show the self oscillation energies A_1 , E_1 and E_2 (low) observed from the Raman light scattering of ZnO. (b) Phonon density of states.

temperatures of 300 and 120 K at frequencies of 9,852 and 9,450 MHz, respectively, with the direction of the magnetic field induction vector both parallel and perpendicular to the optical axis C of the samples. The PL spectra in the area of the A line and its vibrational replicas were recorded on a Fluorolog3 spectrofluorometer (Horiba) equipped with a cryogenic system capable of cooling to a temperature of 4.2 K. A built-in xenon lamp was used for excitation, the light of which was passed through a monochromator. The spectral resolution was 0.5 cm^{-1} . The PL spectra were recorded using a Rochon prism polarizer, through which radiation was passed to polarize the light emerging from the sample, and then the radiation was incident on a photodetector. Polarized light should be used because the crystal under study is uniaxial. Light can be polarized: either the electric vector of the light wave \mathbf{E} is parallel to the crystallographic axis C of the sample ($\mathbf{E} \parallel \mathbf{C}$, π -polarization), or perpendicular ($\mathbf{E} \perp \mathbf{C}$, σ -polarization).

Findings and discussion

Fig. 1, a shows the PL spectra of a ZnO:Mn sample with a residual Fe impurity at a temperature $T = 4.5$ K in the interval of $12660\text{--}14700 \text{ cm}^{-1}$ for σ - and π -polarizations of radiation. Meanwhile, the position of the zero-phonon line A (14426.43 cm^{-1}) is taken as zero, then the modulus of the difference between the energy positions of the corresponding replicas and the zero-phonon line itself is plotted along the energy axis. For both polarizations, the spectra consist of a zero-phonon line A and a series of vibrational repetitions of this line. The A line is due to the intracenter transition ${}^4T_1 \rightarrow {}^6A_1$ of the $\text{Fe}^{3+}(d^5)$ ion, as was shown in [3]. The impurity of manganese does not change the positions of the lines, but the lines themselves look broadened in comparison with the data of the paper [3]. Apparently, the broadening arises precisely due to manganese ions. The structure of the vibrational repetitions for both polarizations is very similar, only for the doublet satellite 3, with σ polarization, the low-energy component has a much higher intensity than the high-energy one, while in case of π polarization, the intensities of both components are approximately the same. These spectra differ significantly from the PL spectra of the II–VI:Mn compounds, where, as a rule, there is a fairly wide band with a sharp rise and a smooth decay, due to the intracenter transition $T_1 \rightarrow {}^6A_1$. The broad bands of the intracenter PL are due to transitions with a change in the ratio of the numbers of t_2 - and e electrons of the 3d shell of the d^5 configuration, for example, $2t_2 + 3e \rightarrow 3t_2 + 2e$. This is the transition ${}^4T_1 \rightarrow {}^6A_1$, and therefore it is accompanied by many emitted phonons [7]. It can be noted that, in our case, intense vibrational repetitions have a background component characteristic for the PL of II–VI:Mn compounds.

Oscillations of the ZnO lattice are characterized by the movement of ions of a primitive cell consisting of two Zn^{2+} ions and two O^{2-} ions. These oscillations are called eigenmodes and occur either along the C crystallographic axis or perpendicular to this axis. They are classified as $A_1(\text{TO})$, $A_1(\text{LO})$, B_1 , $E_1(\text{TO})$, $E_1(\text{LO})$, E_2 (low), E_2 (high) [8,9]. Intense vibrational repetitions are due to the specifics of the $\text{Fe}^{3+}(d^5)$ ions and its nearest environment. Fig. 1, a also shows a comparison of the energies of the vibrational repetitions with the energies of the characteristic oscillations A_1 , B_1 , E_1 , E_2 . It is clearly seen that the frequency of the phonon replica 4 does not coincide with the frequencies of the eigenmodes.

Fig. 1 shows a comparison of the PL spectra of ZnO:Mn with an uncontrolled Fe impurity with the density of states of phonons of the zinc oxide lattice according to the data of [10]; the latter is shown at the bottom of Fig. 1, b. It can be seen that the 1 and 2 satellites approximately correspond to the maxima of the density of states. The maxima of the satellites 3 are located at the very beginning of one of the branches of the density of states, and the most intense satellite 4 falls into a dip between two branches of the density of phonon states of the lattice, where this density is

there is no understanding of the frequency of the peaks, their much greater width compared to the line of the intracenter transition ${}^4T_1 \rightarrow {}^6A_1$).

Funding

The work was carried out as part of the state assignment of MINOBRNAUKI of Russia (topic „Electron“, № 122021000039-4, FEUZ-2020-0059 project and topic „Quantum“ № 122021000038-7 FEUZ-2023-0017 project), RSF project № 21-12-00392 and as part of the state assignment of the ISSP of the RAS, as well as with the financial support of the MINOBRNAUKI of the Russian Federation as part of the Ural Federal University Development Program in accordance with the program of strategic academic leadership „Priority-2030“.

Conflict of interest

The authors declare that they have no conflict of interest.

References

- [1] V.I. Sokolov, N.B. Gruzdev, V.A. Vazhenin, A.V. Fokin, A.V. Druzhinin. *Phys. Solid State*, **61** (5), 702 (2019). DOI: 10.1134/S1063783419050354.
- [2] V.I. Sokolov, N.B. Gruzdev, V.A. Vazhenin, A.V. Fokin, A.V. Korolev, V.V. Menshenin. *J. Exp. and Theor. Phys.*, **130** (5), 681 (2020). DOI: 10.1134/S1063776120040123.
- [3] R. Heitz, A. Hoffmann, I. Broser. *Phys. Rev. B*, **45** (16), 8977 (1992).
- [4] D. V. Azamat, J. Debus, D. R. Yakovlev, V.Yu. Ivanov, M. Godlewski, M. Fanciulli, M. Bayer. *Phys. Status Solidi B*, **247** (6), 1517–1520 (2010). DOI: 10.1002/pssb.200983224
- [5] D.V. Azamat, M. Fanciulli. *Physica B*, **401–402**, 382–385 (2007). DOI: 10.1016/j.physb.2007.08.193
- [6] R.D. Shannon. *Acta Cryst.*, **A32**, 751 (1976).
- [7] D.T. Sviridov, Yu.F. Smirnov. *Theory of optical spectra of transition metals* (Nauka, Moscow, 1977). (in Russian).
- [8] C.F. Klingshirn, B.K. Meyer, A. Waag, A. Hoffman, J. Geyrts. *Zinc Oxide* (Springer, Heidelberg, 2010).
- [9] H. Morkoç, Ü. Özgür. *Zinc Oxide* (WILEY-VCN Verlag, Weinheim, 2009).
- [10] J. Serrano, A.H. Romero, F.J. Manjon, R. Lauck, M. Cardona, A. Rubio. *Phys. Rev. B*, **69**, 094306 (2004). DOI: 10.1103/Phys. Rev. B. 69.094306
- [11] V.J. Schneider. *Z. Naturforschg*, **17 a**, 189?190 (1962).
- [12] W.C. Holton, M. de Wit, T.L. Estle. *Phys. Rev.*, **169** (2), 359-372 (1968).
- [13] Yu.S. Kutin, G.V. Mamin, S.B. Orlinskii. *J. Magnetic Resonance*, **237**, 110–114 (2013).

Translated by E.Potapova