

Figure 2. *a* — amplitude of emitted signal $g(x, y)$; *b* — radiator ultrasound image $r(x, y)$: *C* — inhomogeneity; *d* — inhomogeneity *C* size; *L, R* — responses emitted by inhomogeneity *C*; *D* — surface defect; *E* — piezoelectric wafer edge.

The matching circuit at the radiator input enabled obtaining the operating frequency band of about 60–100 MHz. In this frequency band, the transducer was excited by video pulses about 5 ns long produced by generator 5. The radiator was in contact with immersion liquid 6 which was deionized water. Longitudinal waves that may arise from the transformation of shear vibrations in the region of radiator inhomogeneities propagated in water and were received by focusing ultrasonic transducer 7. The transducer's central frequency and relative bandwidth were 75 MHz and 65%, respectively, which ensured efficient reception of the radiated pulse waves. The pulsed operating mode allowed extraction in the time domain of the useful signal against the background interference generated by the probing ultrasonic pulse and its re-reflections. After amplification, filtering and analog-to-digital conversion in the electronic unit 8, the received signals were fed to the computer. Transducer 7 was focused on the radiator 1 surface, which provided transverse spatial resolution of $\sim 20\mu\text{m}$. The ultrasound absorption coefficient in water at the frequency of 100 MHz was 2.2 dB/mm, while the wave path in liquid was equal to the transducer focal length (3.4 mm). Thus, the signal attenuation in liquid did not exceed 7.5 dB and did not critically affect the method sensitivity. To measure the spatial distribution of received responses $g(x, y)$, the transducer was mechanically scanned in plane (x, y) .

The described experimental setup was built based on the scanning acoustic microscope; its more detailed description is given in [4]. The ultrasound images of inhomogeneities were constructed in the standard echo-pulse mode of the acoustic microscope. Generator 5 was connected to transducer 7 that emitted probing focused waves and received responses $r(x, y)$ reflected from the object.

Spatial distribution of the transducer-emitted signal $g(x, y)$ amplitude is presented in Fig. 2, *a*. The received

responses are located in a well-defined region corresponding to upper electrode 4 (Fig. 1). The width of this region is equal to the electrode width (2.4 mm). The responses have different shapes and sizes and are unevenly distributed across the region. Note that inhomogeneities on the entire piezoelectric wafer surface are not visible in the radiator optical images, except for large defect *D*. In the ultrasound $r(x, y)$ image (Fig. 2, *b*) obtained in the echo-pulse mode of the acoustic microscope, defect *D* is also observed, but the upper radiator electrode is invisible because of its low thickness. Its location is shown by the dashed line. Besides large defect *D*, the figure's upper panel demonstrates uneven edge *E* of the lithium niobate wafer, over almost entire surface of which responses from small inhomogeneities are distributed. Temporal structure of the incoming ultrasonic signals shows that those inhomogeneities are located in the vicinity of the wafer-to-sound duct interface (see Fig. 1). Their sizes and positions match those of responses in the $g(x, y)$ image formed by the transformation of shear vibrations (Fig. 2, *a*). It is important to note that only those defects that are located under the electrode contribute to the $g(x, y)$ signal. Thus, signals are generated not over the entire piezoelectric wafer surface but just in the shear wave radiator. As the image of $r(x, y)$ shows (Fig. 2, *b*), the defects are predominantly round in shape. Responses emitted by the piezoelectric wafer (Fig. 2, *a*) also have a rounded outer boundary, but they are divided into two parts. For instance, inhomogeneity *C* in the $r(x, y)$ image corresponds to response $g(x, y)$ exhibiting well-distinguished halves *L* and *R* (Fig. 2, *a*).

Fig. 3, *a* presents the spatial-temporal structure of signal $g(x, t)$ recorded as a function of coordinate x and time t . The signal is recorded along the dashed line (Fig. 2, *a*) passing through the defect. The signal value is represented by shades of gray; the light shade corresponds to the positive

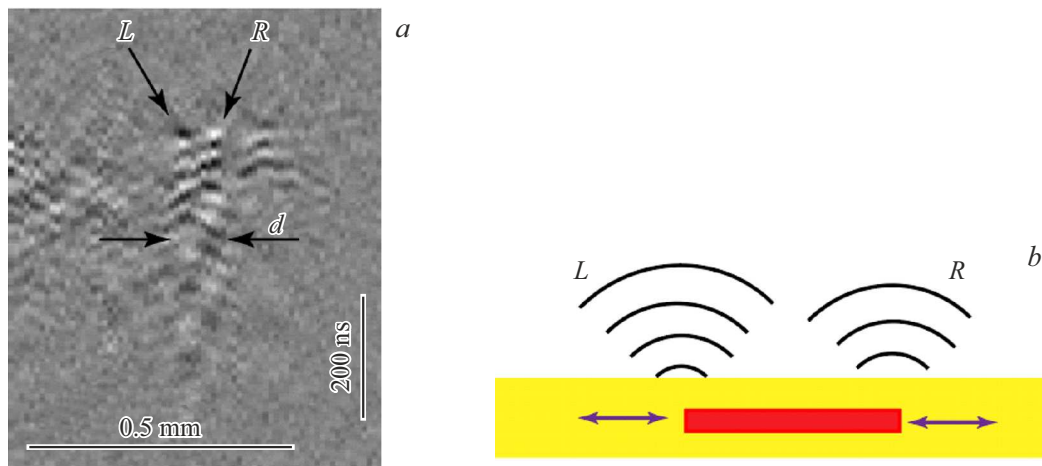


Figure 3. *a* — signal $g(x, t)$ measured in the vicinity of inhomogeneity; *b* — schematic diagram of the longitudinal wave generation in liquid.

signal polarity, while the dark shade represents the negative polarity. The response arrival time corresponds to the time of the longitudinal ultrasonic wave propagation from radiator 1 to receiving transducer 7 (Fig. 1). Response size d is approximately $140\ \mu\text{m}$, the vibration period in the received wave packet is about 15 ns, which is consistent with the frequency range of the ultrasonic emitter and receiver. In the received response, components L and R (Fig. 3, *a*) located above the defect edges are distinguished, while in its center the signal is almost fully absent. It is also important to note that components L and R are opposite in polarity.

Behavioral features of the generated signals may be qualitatively explained as follows (Fig. 3, *b*). When horizontally polarized shear motions interact in the radiator material with inhomogeneity edges, the tangential deformation field gets distorted and the vertical deformation component arises on the interface between the radiator and immersion liquid. This component gives rise to radiation into liquid of the longitudinal wave which is received by the focusing transducer. Since at any given time moment exciting oscillations at the defect edges are directed oppositely relative to its center, polarities of the L and R responses are also inverted. In addition, the signal generation is low in the vicinity of inhomogeneity passing through its center and extending along axis y perpendicular to shear vibrations.

Thus, it has been experimentally shown that inhomogeneities in the structure of piezoelectric shear wave radiators may be detected and visualized in the immersion measurement scheme by converting shear vibrations into longitudinal waves in liquid. This method may be used to study the properties of shear wave radiators, develop their fabrication procedure, and control their quality. In this work, studies were performed for a lithium niobate radiator mounted on a paratellurite substrate. This structure is often employed in acousto-optic devices; however, the method field of application seems to be wider. What is important is that the visualized inhomogeneities caused distortion

of shear vibrations and generation of a longitudinal wave whose amplitude is sufficient to make it detectable. Thus, the method may be applied for various substrate and radiator materials, including piezoceramics, and for various frequency ranges.

Funding

The study was supported by the RF Ministry of Science and Higher Education, State Assignment FFNS-2025-0006.

Conflict of interests

The authors declare that they have no conflict of interests.

References

- [1] W. Ding, M. Bavencoffe, M. Lethicq, *Materials*, **14** (9), 2269 (2021). DOI: 10.3390/ma14092269
- [2] B. Lin, V. Giurgiutiu, P. Pollock, B. Xu, J. Doane, *AIAA J.*, **48** (3), 635 (2010). DOI: 10.2514/1.44776
- [3] A.Z. Kaloev, D.A. Nikolaev, V.A. Khokhlova, S.A. Tsysar, O.A. Sapozhnikov, *Acoust. Phys.*, **68** (1), 71 (2022). DOI: 10.1134/S1063771022010043.
- [4] S.A. Titov, A.S. Machikhin, V.Ed. Pozhar, *Materials*, **15** (5), 1792 (2022). DOI: 10.3390/ma15051792
- [5] J.N. Eiras, L. Gavérina, J.-M. Roche, *Sensors*, **24** (2), 450 (2024). DOI: 10.3390/s24020450
- [6] L. Svilainis, D. Kybartas, A. Aleksandrovas, T.E.G. Alvarez-Arenas, *NDT E Int.*, **116**, 102360 (2020). DOI: 10.1016/j.ndteint.2020.102360

Translated by EgoTranslating